Republic of Kenya

EDICT OF GOVERNMENT

In order to promote public education and public safety, equal justice for all, a better informed citizenry, the rule of law, world trade and world peace, this legal document is hereby made available on a noncommercial basis, as it is the right of all humans to know and speak the laws that govern them.

KS 184-5 (2012) (English): Primary batteries — Specification, Part 5: Safety of batteries with aqueous electrolyte (Draft Standard)

BLANK PAGE

PROTECTED BY COPYRIGHT

Kenya Bureau of Standards
Quality products for quality life

KEBS Head Office
P.O. Box 54974, Nairobi 00200
Tel: +254 (0) 20 605490,605506,
Mobile: 0722 202 137/8.
0734 600 471/1
Fax: +254 (0) 20 609 660
Direct Dial: +254 (0) 20 694 8000
E-mail: infor@kebs.org
Web: http://www.kebs.org

KEBS Coast Region
P.O. Box 99376, Mombasa 80100
Tel: +254 (0) 41 229 563, 230 939/40
Fax: +254 (0) 41 229 448
E-mail: kebs-msa@kebs.org

KEBS Lake Region
P.O. Box 2949, Kisumu 40100
Tel: +254 (0) 57 202 8396, 202 9549
Fax: +254 (0) 57 202 7814
E-mail: kebs-kisumu@kebs.org

KEBS Rift Valley Region
P.O. Box 2138, Nakuru 20100
Tel: +254 (0) 51221 0553/5, 221 1208
Fax: +254 (0) 51221 0076
E-mail: kebs-nakuru@kebs.org

KEBS Mt. Kenya Region
P.O. Box 1790, Nyeri 10100
Tel: +254 (0) 61 203 1410/1
Fax: +254 (0) 61 203 2038
Email: kebs-nyeri@kebs.org

KEBS North Eastern Rgion
P.O. Box 978, Garissa 70100
Tel: +254 (0) 46 2519
Fax: +254 (0) 46 3455
E-mail: kebs-garissa@kebs.org

Ref.: KS 184-4:2012 **Date: 2012-04-05**

Title:	KS 184-5:2012, Primary batteries – Part 5: Safety of batteries with aqueous electrolyte	
Document Type:	Public Review Comments	
Dates:	Circulation date	Closing date
	2012-04-05	2012-05-05

PUBLIC REVIEW DRAFT KS184-4:2012, PRIMARY BATTERIES – PART 5: SAFETY OF BATTERIES WITH AQUEOUS ELECTROLYTE

This Draft Kenya Standard has been prepared by the Extra Low Voltage Equipment Technical Committee in accordance with the procedures of the Bureau, and is now being circulated for public comments.

The Committee would appreciate any comments on this Draft Standards, which should be submitted before **2012-05-05** using the attached template. It will also be appreciated if those who have no specific comments to make but find the draft standard generally acceptable can notify us accordingly. Absence of any reply or comments shall be deemed to be an acceptance of the technical contents of the draft Kenya standard and **shall constitute an approval vote**.

Suggestions entailing amendments of the text should include wording preferred and the relevant clause number quoted against any comments made.

This draft standard is subject to change and should not be referred to or used as a Kenya Standard.

All correspondence pertaining to this draft standard should be addressed to the Managing Director, Kenya Bureau of Standards for the attention of **Zacheus Mwatha**.

Yours faithfully,

Zacheus Mwatha
For: DIRECTOR
STANDARDS DEVELOPMENT AND INTERNATIONAL TRADE
ZIM/li

DRAFT KENYA STANDARD **KS 184-5:2012**

PUBLIC REVIEW DRAFT

Primary batteries — Specification
Part 5: Safety of batteries with aqueous electrolyte

PUBLIC REVIEW DRAFT

PUBLIC REVIEW DRAFT, APRIL 2012

© KEBS 2012 — All rights reserved Second Edition 2012

TECHNICAL COMMITTEE REPRESENTATION

The following organizations were represented in the technical committee.

Motor Vehicle Inspection Unit
Matatu Owners Association
Speed Governors and Road Safety Association
Saferider Management Systems Limited
Markmann's Company Ltd.
Pinnacle Systems
Kenya Police
Ministry of Roads
Communications Commission of Kenya
National Communications Secretariat
General Electric
Chloride Exide
Associated Battery Manufacturers East Africa Ltd.
Standard Chartered Bank
Kenya Pipeline Company
Eveready East Africa Ltd
Frontier Power
Kenya Bureau of Standards - Secretariat

REVISION OF KENYA STANDARDS

In order to keep abreast of progress in industry, Kenya Standards shall be regularly reviewed. Suggestions for improvements to published standards, addressed to the Managing Director, Kenya Bureau of Standards, are welcome.

© Kenya Bureau of Standards, 2012

Copyright: Users are reminded that by virtue of section 6 of the Copyright Act, Cap. 130 of the Laws of Kenya, copyright subsists in all Kenya Standards and except as provided under section 7 of this Act, no Kenya Standard produced by Kenya Bureau of Standards may be reproduced, stored in a retrieval system in any form or transmitted by any means without prior permission in writing from the Managing Director.

KENYA BUREU OF STANDARDS (KEBS)

Head Office: P.O. Box 54974 Nairobi,Tel.: (+ 254 020) 605490, 603433, 602350/1, 603352,Fax: (+ 254 020) 604031

E-Mail: info@kebs.org, **Web:http**://www.kebs.org

Coast Regional Office
P.O. Box 99376, Mombasa
Tel.: (+254 041) 229563, 230939/40
Fax: (+254 041) 229448

Western Kenya Regional Office
P.O. Box 2949, Kisumu
Tel.: (+254 057) 23549, 22396
Fax: (+254 057) 21814

Rift Valley Regional Office
P.O. Box 8111, Eldoret
Tel.: (+254 053) 33151, 63377
Fax: (+254 053) 33150

 © KEBS 2012 — All rights reserved

PUBLIC REVIEW DRAFT

Primary batteries — Specification
Part 5: Safety of batteries with aqueous electrolyte

PUBLIC REVIEW DRAFT

KENYA BUREU OF STANDARDS (KEBS)

Head Office: P.O. Box 54974 Nairobi,Tel.: (+ 254 020) 605490, 603433, 602350/1, 603352,Fax: (+ 254 020) 604031

E-Mail: info@kebs.org, **Web:http**://www.kebs.org

Coast Regional Office
P.O. Box 99376, Mombasa
Tel.: (+254 041) 229563, 230939/40
Fax: (+254 041) 229448

Western Kenya Regional Office
P.O. Box 2949, Kisumu
Tel.: (+254 057) 23549, 22396
Fax: (+254 057) 21814

Rift Valley Regional Office
P.O. Box 8111, Eldoret
Tel.: (+254 053) 33151, 63377
Fax: (+254 053) 33150

© KEBS 2012 — All rights reserved

Foreword

This Kenya Standard has been prepared by the Extra-Low Voltage Equipment Technical Committee under the guidance of the Standards Projects Committee and is in accordance with the procedures of the Bureau.

This is the first revision of KS 184 and in this revision the committee has retained the structure of IEC 60086 by covering the standard in 5 parts in separate documents, this part being Part 5, as follows:

KS04-184: Kenya Standard Specification for Primary Batteries.
- Part 1: General
- Part 2: Physical and electrical specifications
- Part 3: Watch batteries
- Part 4: Safety of lithium batteries
- **Part 5: Safety of batteries with aqueous electrolyte**

This Part 4 has been aligned with IEC 60086-4:2007. Where any text differs from the IEC text, this is indicated by a vertical line in the right hand margin.

Acknowledgement is hereby made for the use of IEC 60086-5:2011 in this standard.

For the purpose of this Kenya Standard, the source text should be/has been modified as follows:

(a) The words “this Kenya Standard” should replace “this International Standard” whenever they appear.

(b) A full point (.) has been used in place of a comma (,) when referring to a decimal marker.

(c)References to international standards should be replaced by references to the following equivalent Kenya Standards:

Reference to International Standard		Kenya Standard	
No.	Title	No.	Title
IEC 60086-2	Primary batteries - Part 2: Physical and electrical specifications	KS 184: Part 2	Primary batteries. Part 2: Physical and electrical specifications.
IEC 60086-3	Primary batteries - Part 3: Watch batteries	KS 184: Part 3	Primary batteries. Part 3: Watch batteries
IEC 60086-4	Primary batteries - Part 4: Safety of lithium batteries	KS 184: Part 4	Primary batteries. Part 4: Safety of lithium batteries
IEC 60086-5	Primary batteries - Part 5: Safety of batteries with aqueous electrolyte	KS 184: Part 5	Primary batteries. Part 5: Safety of batteries with aqueous electrolyte
IEC 60410	Sampling plans and procedures for inspection by attributes.	-	-
IEC 61429	Marking of secondary cells and batteries with the international recycling symbol ISO 7000-1135	-	-
ISO 3951	Sampling procedures and charts for inspection by variables for percent non-conforming.	KS ISO 3951	Sampling procedures and charts for inspection by variables for percent non-confirming.
ISO/IEC Directives – Part 2		-	-

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

This third edition cancels and replaces the second edition (2005) and constitutes a technical revision.

The major technical changes with respect to the previous edition are the test requirements and the harmonization of the marking clause with the other standards of the IEC 60086 series. Moreover, the table of safety pictograms was added as Annex C.

PUBLIC REVIEW DRAFT

© KEBS 2012 — All rights reserved

INTRODUCTION

The concept of safety is closely related to safeguarding the integrity of people and property. This part of IEC 60086 specifies tests and requirements for primary batteries with aqueous electrolyte and has been prepared in accordance with ISO/IEC guidelines, taking into account all relevant national and international standards which apply. Also included in this standard is guidance for appliance designers with respect to battery compartments and information regarding packaging, handling, warehousing and transportation.

Safety is a balance between freedom from risks of harm and other demands to be met by the product. There can be no absolute safety. Even at the highest level of safety, the product can only be relatively safe. In this respect, decision-making is based on risk evaluation and safety judgment.

As safety will pose different problems, it is impossible to provide a set of precise provisions and recommendations that will apply in every case. However, this standard, when followed on a judicious "use when applicable" basis, will provide reasonably consistent standards for safety.

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

1 Scope

This part of IEC 60086 specifies tests and requirements for primary batteries with aqueous electrolyte to ensure their safe operation under intended use and reasonably foreseeable misuse.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

KS 184-1:2011, *Primary batteries – Part 1: General*

KS 184-2:2011, *Primary batteries – Part 2: Physical and electrical specifications*

IEC 60068-2-6, *Environmental testing – Part 2-6: Tests – Test Fc : Vibrations (sinusoidal)*

IEC 60068-2-27, *Environmental testing – Part 2-27: Tests – Test Ea and guidance: Shock*

IEC 60068-2-31, *Environmental testing – Part 2-31: Tests – Test Ec: Rough handling shocks, primarily for equipment-type specimens*

3 Terms and definitions

For the purpose of this document, the terms and definitions given in IEC 60086-1 as well as the following terms and definitions apply.

3.1
battery
one or more cells electrically connected by permanent means, fitted in a case, with terminals, markings and protective devices etc, as necessary for use
[IEC 60050-482: 2004, 482-01-04, modified]

3.2
button battery
small round battery, where the overall height is less than the diameter; batteries complying with Figures 3 and 4 of KS 184-2

3.3
cell
basic functional unit, consisting of an assembly of electrodes, electrolyte, container, terminals and usually separators that is a source of electric energy obtained by direct conversion of chemical energy
[IEC 60050-482: 2004, 482-01-01]

3.4
cylindrical (cell or battery)
cell or battery with a cylindrical shape in which the overall height is equal to or greater than the diameter
[IEC 60050-482: 2004, 482-02-39, modified]

3.5
explosion (battery explosion)
an instantaneous release wherein solid matter from any part of the battery is propelled to a distance greater than 25 cm away from the battery

© KEBS 2012 — All rights reserved

PUBLIC REVIEW DRAFT

3.6
harm
physical injury or damage to the health of people.
[ISO/IEC Guide 51:1999, 3.3]

3.7
hazard
potential source of harm
[ISO/IEC Guide 51:1999, 3.5]

3.8
intended use
use of a product, process or service in accordance with information provided by the supplier
[ISO/IEC Guide 51:1999, 3.13]

3.9
leakage
unplanned escape of electrolyte, gas or other material from a cell or battery
[IEC 60050-482: 2004, 482-02-32]

3.10
nominal voltage (of a primary battery)
V_n (symbol)
suitable approximate value of the voltage used to designate or identify a cell, a battery or an electrochemical system
[IEC 60050-482: 2004, 482-03-31, modified]

3.11
primary (cell or battery)
cell or battery that is not designed to be electrically recharged

3.12
prismatic (cell or battery)
cell or battery having the shape of a parallelepiped whose faces are rectangular
[IEC 60050-482: 2004, 482-02-38, modified]

3.13
protective device
device such as a fuse, a diode or other electric or electronic current limiter designed to interrupt the current flow in an electrical circuit

3.14
reasonably foreseeable misuse
use of a product, process or service in a way not intended by the supplier, but which may result from readily predictable human behaviour
[ISO/IEC Guide 51:1999, 3.14]

3.15
risk
combination of the probability of occurrence of harm and the severity of that harm
[ISO/IEC Guide 51:1999, 3.2]

3.16
round (cell or battery)
cell or battery with circular cross section

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

3.17
safety
freedom from unacceptable risk
[ISO/IEC Guide 51:1999, 3.1]

3.18
undischarged
state of charge of a primary cell or battery corresponding to 0 % depth of discharge

3.19
venting
release of excessive internal pressure from a battery in a manner intended by design to preclude explosion

4 Requirements for safety

4.1 Design

4.1.1 General

Batteries shall be so designed that they do not present a safety hazard under conditions of normal (intended) use.

4.1.2 Venting

All batteries shall incorporate a pressure relief feature or shall be so constructed that they will relieve excessive internal pressure at a value and rate which will preclude explosion. If encapsulation is necessary to support cells within an outer case, the type of encapsulant and the method of encapsulation shall not cause the battery to overheat during normal operation nor inhibit the operation of the pressure relief feature.

The battery case material and/or its final assembly shall be so designed that, in the event of one or more cells venting, the battery case does not present a hazard in its own right.

4.1.3 Insulation resistance

The insulation resistance between externally exposed metal surfaces of the battery excluding electrical contact surfaces and either terminal shall be not less than 5 MΩ at $500\ ^{+100}_{0}$ V .

4.2 Quality plan

The manufacturer shall prepare a quality plan defining the procedures for the inspection of materials, components, cells and batteries during the course of manufacture, to be applied to the total process of producing a specific type of battery.

5 Sampling

5.1 General

Samples should be drawn from production lots in accordance with accepted statistical methods.

5.2 Sampling for type approval

The number of samples drawn for type approval is given in Figure 1.

PUBLIC REVIEW DRAFT

© KEBS 2012 — All rights reserved

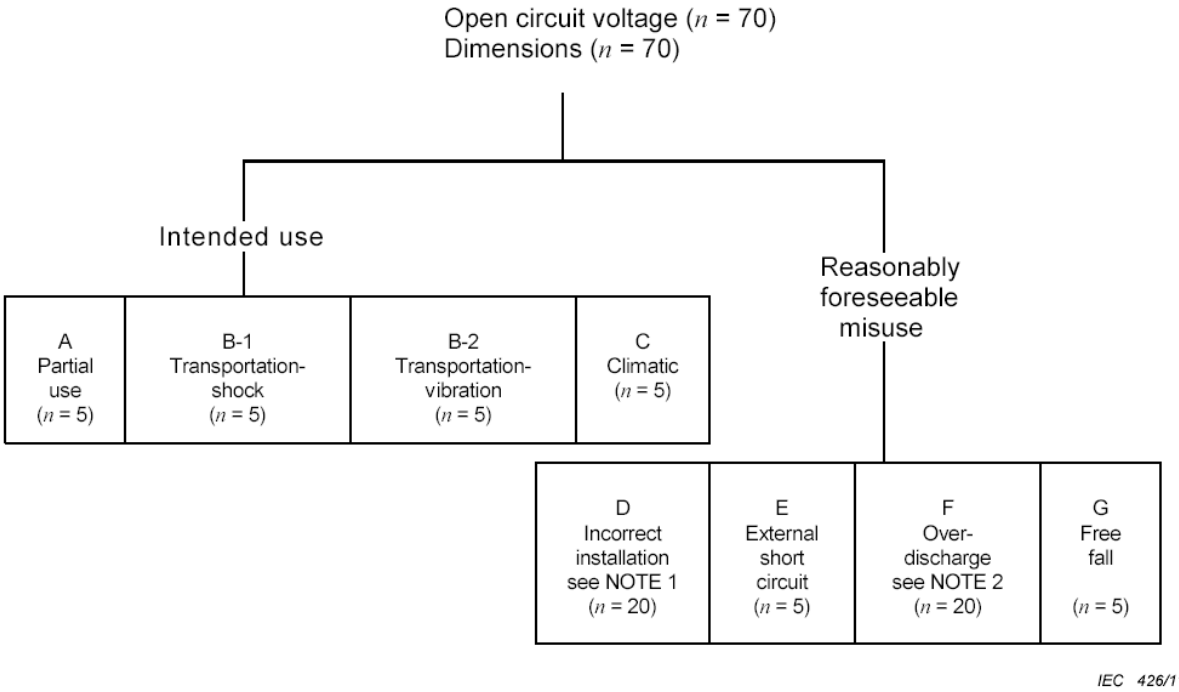

NOTE 1 Four batteries connected in series with one of the four batteries reversed (5 sets).
NOTE 2 Four batteries connected in series, one of which is discharged (5 sets).

Figure 1 – Sampling for type approval tests and number of batteries required

6 Testing and requirements

6.1 General

6.1.1 Applicable safety tests

Applicable safety tests are shown in Table 1.

The tests described in Tables 2 and 6 are intended to simulate conditions which the battery is likely to encounter during intended use and reasonably foreseeable misuse.

PUBLIC REVIEW

 © KEBS 2012 — All rights reserved

Table 1 – Test matrix

System letter	Negative electrode	Electrolyte	Positive electrode	Nominal voltage per cell V	Form	Applicable tests						
						A	B-1 B-2	C	D	E	F	G
No letter	Zinc (Zn)	Ammonium chloride, Zinc chloride	Manganese dioxide (MnO_2)	1,5	R	x	x	x	x	x	x	x
					B	NR						
					Pr	x	x	x	x	x	x	x
					M	x	x	x	NR	x	x	x
A	Zinc (Zn)	Ammonium chloride, Zinc chloride	Oxygen (O_2)	1,4	R	x	x	x	NR	x	x	x
					B	NR						
					Pr	x	x	x	x	x	x	x
					M	x	x	x	NR	x	x	x
L	Zinc (Zn)	Alkali metal hydroxide	Manganese dioxide (MnO_2)	1,5	R	x	x	x	x	x	x	x
					B	x	x	x	NR	x	NR	x
					Pr	x	x	x	x	x	x	x
					M	x	x	x	NR	x	NR	x
P	Zinc (Zn)	Alkali metal hydroxide	Oxygen air (O_2)	1,4	R	NR						
					B	NR	x	x	NR	x	NR	x
					Pr	x	x	x	x	x	x	x
					M	NR						
S	Zinc (Zn)	Alkali metal hydroxide	Silver oxide (Ag_2O)	1,55	R	x	x	x	NR	x	NR	x
					B	x	x	x	NR	x	NR	x
					Pr	x	x	x	x	x	x	x
					M	NR						

Test description:

A: storage after partial use

B-1: transportation-shock

B-2: transportation-vibration

C: climatic-temperature cycling

D: incorrect installation

E: external short circuit

F: overdischarge

G: free fall

Key

R: cylindrical (3.4)

B: button (3.2)

Pr: prismatic single cell (3.12)

M: multicell

x: required

NR: Not required

Systems L and S button cells or batteries under 250 mAh capacity and system P button cells or batteries under 700 mAh capacity are exempt from any testing.

© KEBS 2012 — All rights reserved

6.1.2 Safety notice

WARNING

These tests call for the use of procedures which may result in injury if adequate precautions are not taken.

It has been assumed in the drafting of these tests that their execution is undertaken by appropriately qualified and experienced technicians using adequate protection.

6.1.3 Ambient temperature

Unless otherwise specified, these tests shall be carried out at (20 ± 5) ℃.

6.2 Intended use

6.2.1 Intended use tests and requirements

Table 2 – Intended use tests and requirements

Test		Intended use simulation	Requirements
Electrical test	A	Storage after partial use	No leakage (NL) No fire (NF) No explosion (NE)
Environmental tests	B-1	Transportation-shock	No leakage (NL) No fire (NF) No explosion (NE)
	B-2	Transportation-vibration	No leakage (NL) No fire (NF) No explosion (NE)
Climatic-temperature	C	Climatic-temperature cycling	No fire (NF) No explosion (NE)

6.2.2 Intended use test procedures

6.2.2.1 Test A – Storage after partial use

a) Purpose

This test simulates the situation when an appliance is switched off and the installed batteries are partly discharged. These batteries may be left in the appliance for a long time or they are removed from the appliance and stored for a long time.

b) Test procedure

An undischarged battery is discharged under an application/service output test condition, with the lowest resistive load test as defined in IEC 60086-2 until the service life falls by 50 % of the minimum average duration (MAD) value, followed by storage at (45 ± 5) ℃ for 30 days.

c) Requirements

There shall be no leakage, no fire and no explosion during this test.

6.2.2.2 Test B-1 – Transportation-shock

a) Purpose

 © KEBS 2012 — All rights reserved

This test simulates the situation when an appliance is carelessly dropped with batteries installed in it. This test condition is generally specified in IEC 60068-2-27.

b) Test procedure

An undischarged battery shall be tested as follows.

The shock test shall be carried out under the conditions defined in Table 3 and the sequence in Table 4.

Shock pulse – The shock pulse applied to the battery shall be as follows:

Table 3 – Shock pulse

Acceleration		Waveform
Minimum average acceleration first three milliseconds	Peak acceleration	
75 g_n	125 g_n to 175 g_n	Half sine
NOTE g_n = 9,80665 m/s².		

Table 4 – Test sequence

Step	Storage time	Battery orientation	Number of shocks	Visual examination periods
1	–	–	–	Pre-test
2	–	[a]	1 each	–
3	–	[a]	1 each	–
4	–	[a]	1 each	–
5	1 h	–	–	–
6	–	–	–	Post-test
[a] The shock shall be applied in each of three mutually perpendicular directions.				

Step 1 Record open circuit voltage in accordance with 5.2.
Steps 2 to 4 Apply shock test specified in Table 3 and the sequence in Table 4.
Step 5 Rest battery for 1 h.
Step 6 Record examination results.

c) Requirements

There shall be no leakage, no fire and no explosion during this test.

6.2.2.3 Test B-2 – Transportation-vibration

a) Purpose

This test simulates vibration during transportation. This test condition is generally specified in IEC 60068-2-6.

b) Test procedure

An undischarged battery shall be tested as follows.

© KEBS 2012 — All rights reserved

The vibration test shall be carried out under the following test conditions and the sequence in Table 5.

Vibration – A simple harmonic motion shall be applied to the battery having an amplitude of 0,8 mm, with a total maximum excursion of 1,6 mm. The frequency shall be varied at the rate of 1 Hz/min between the limits of 10 Hz and 55 Hz. The entire range of frequencies (10 Hz to 55 Hz) and return (55 Hz to 10 Hz) shall be traversed in (90 ± 5) min for each mounting position (direction of vibration).

Table 5 – Test sequence

Step	Storage time	Battery orientation	Vibration time	Visual examination periods
1	–	–	–	Pre-test
2	–	a	(90 ± 5) min each	–
3	–	a	(90 ± 5) min each	–
4	–	a	(90 ± 5) min each	–
5	1 h	–	–	–
6	–	–	–	Post-test

[a] The vibration shall be applied in each of three mutually perpendicular directions.

Step 1 Record open circuit voltage in accordance with 5.2.
Steps 2 to 4 Apply the vibration specified in 6.2.2.3 in the sequence in Table 5.
Step 5 Rest battery for 1 h.
Step 6 Record examination results.

c) Requirements

There shall be no leakage, no fire and no explosion during this test.

6.2.2.4 Test C – Climatic-temperature cycling

a) Purpose

This test assesses the integrity of the battery seal which may be impaired after temperature cycling.

b) Test procedure

An undischarged battery shall be tested under the following procedure.

Temperature cycling procedure (see 1) to 7) below and/or Figure 2)

1) Place the batteries in a test chamber and raise the temperature of the chamber to (70 ± 5) ℃ within t_1 = 30 min.
2) Maintain the chamber at this temperature for t_2 = 4 h.
3) Reduce the temperature of the chamber to (20 ± 5) ℃ within t_1 = 30 min and maintain at this temperature for t_3 = 2 h.
4) Reduce the temperature of the chamber to (–20 ± 5) ℃ within t_1 = 30 min and maintain at this temperature for t_2 = 4 h.
5) Raise the temperature of the chamber to (20 ± 5) ℃ within t_1 = 30 min.
6) Repeat the sequence for a further nine cycles.
7) After the 10th cycle, store the batteries for seven days prior to examination.

PUBLIC REVIEW

 © KEBS 2012 — All rights reserved

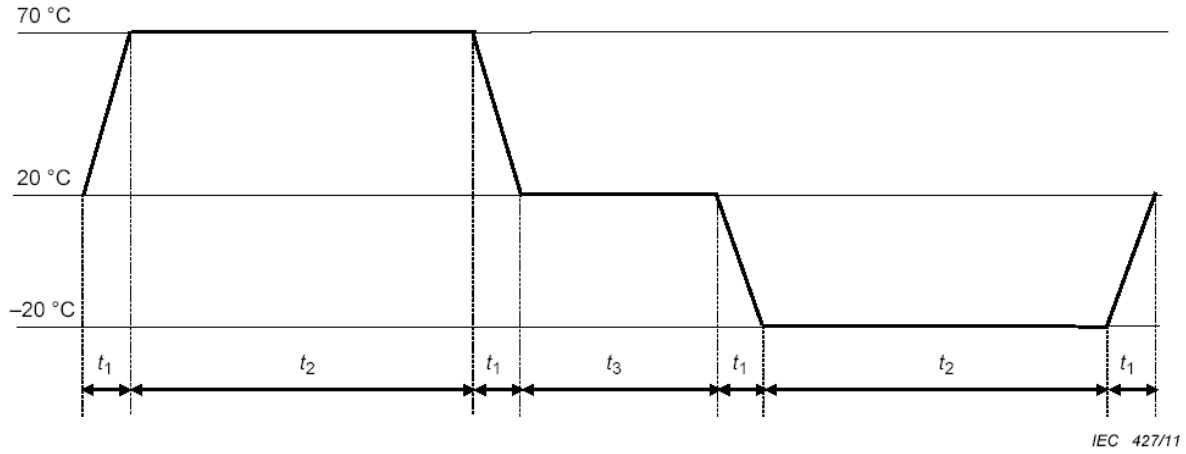

t_1 = 30 min

t_2 = 4 h

t_3 = 2 h

Figure 2 – Temperature cycling procedure

c) Requirements

There shall be no fire and no explosion during this test.

6.3 Reasonably foreseeable misuse

6.3.1 Reasonably foreseeable misuse tests and requirements

Table 6 – Reasonably foreseeable misuse tests and requirements

Test		Misuse simulation	Requirements
Electrical tests	D	Incorrect installation	No fire (NF) No explosion (NE)*
	E	External short circuit	No fire (NF) No explosion (NE)
	F	Overdischarge	No fire (NF) No explosion (NE)
Environmental test	G	Free fall	No fire (NF) No explosion (NE)
* See NOTE 2 of 6.3.2.1b)			

6.3.2 Reasonably foreseeable misuse test procedures

6.3.2.1 Test D – Incorrect installation (four batteries in series)

a) Purpose

This test simulates the condition when one battery in a set is reversed.

b) Test procedure

Four undischarged batteries of the same brand, type and origin shall be connected in series with one reversed (B1) as shown in Figure 3. The circuit shall be completed for 24 h or until the battery case temperature has returned to ambient.

© KEBS 2012 — All rights reserved

The resistance of the inter-connecting circuitry shall not exceed 0,1 Ω.

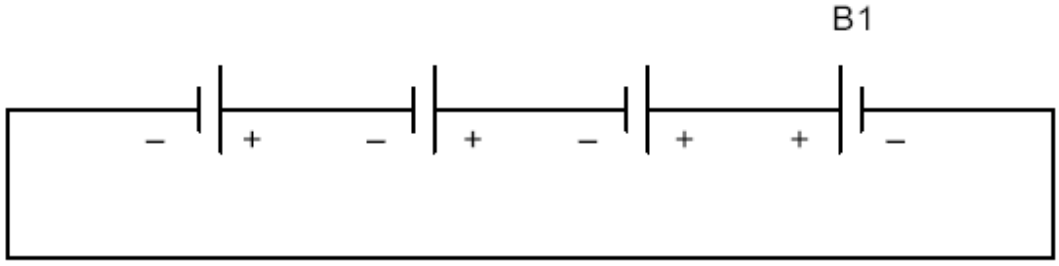

Figure 3 – Circuit diagram for incorrect installation (four batteries in series)

NOTE 1 The circuit in Figure 3 simulates a typical misuse condition.

NOTE 2 Primary batteries are not designed to be charged. However, reversed installation of a battery in a series of three or more exposes the reversed battery to a charging condition. Although cylindrical batteries are designed to relieve excessive internal pressure, in some instances an explosion may not be precluded. Therefore, the user should be clearly advised to install batteries correctly with regard to polarity (+ and –) to avoid this hazard. (See 9.1f)).

c) Requirements

There shall be no fire and no explosion during this test (see NOTE 2 of 6.3.2.1b)).

6.3.2.2 Test E – External short circuit

a) Purpose

This misuse may occur during daily handling of batteries.

b) Test procedure

An undischarged battery shall be connected as shown in Figure 4. The circuit shall be completed for 24 h or until the battery case temperature has returned to ambient. The resistance of the inter-connecting circuitry shall not exceed 0,1 Ω.

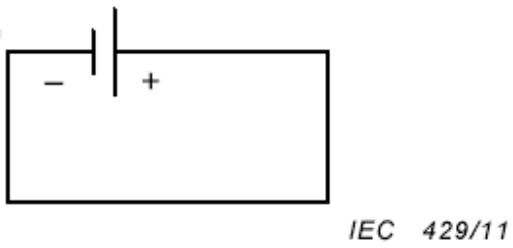

Figure 4 – Circuit diagram for external short circuit

c) Requirements

There shall be no fire and no explosion during this test.

6.3.2.3 Test F – Overdischarge

a) Purpose

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

This test simulates the condition when one (1) discharged battery is series-connected with three (3) other undischarged batteries.

b) Test procedure

One undischarged battery (C1) is discharged under the application or service output test condition, with the highest MAD value (expressed in time units), as defined in IEC 60086-2 until the on-load voltage falls to (*n* x 0,6 V) where *n* is the number of cells in the battery. Then, three undischarged batteries and one discharged battery (C1) of the same brand, type and origin shall be connected in series as shown in Figure 5. The discharge shall be continued until the total on-load voltage falls to four times (*n* x 0,6 V).

The value of the resistor (R1) shall be approximately four times the lowest value from the resistive load tests specified for that battery in IEC 60086-2. The final value of the resistor (R1) shall be the nearest value to that prescribed in 6.4 of IEC 60086-1.

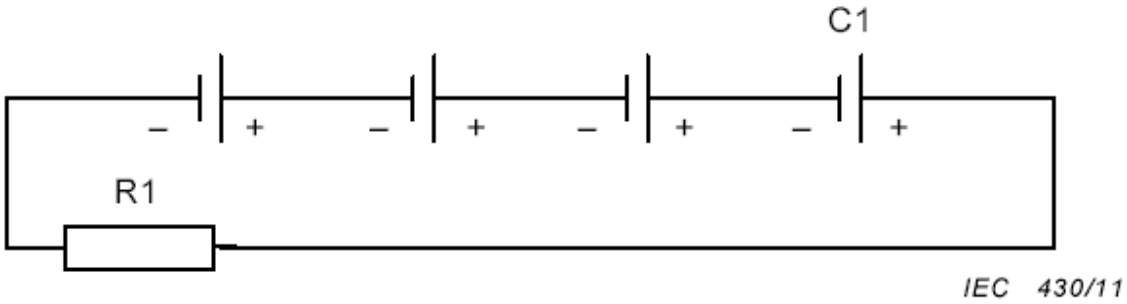

Figure 5 – Circuit diagram for overdischarge

c) Requirements

There shall be no fire and no explosion during this test.

6.3.2.4 Test G – Free fall test

a) Purpose

This test simulates the situation when a battery is accidentally dropped. The test condition is based upon IEC 60068-2-31.

b) Test procedure

Undischarged test batteries shall be dropped from a height of 1 m onto a concrete surface. Each test battery shall be dropped six times, a prismatic battery once on each of its six faces, a round battery twice in each of the three axes shown in Figure 6. The test batteries shall be stored for 1 h afterwards.

PUBLIC REVIEW DRAFT

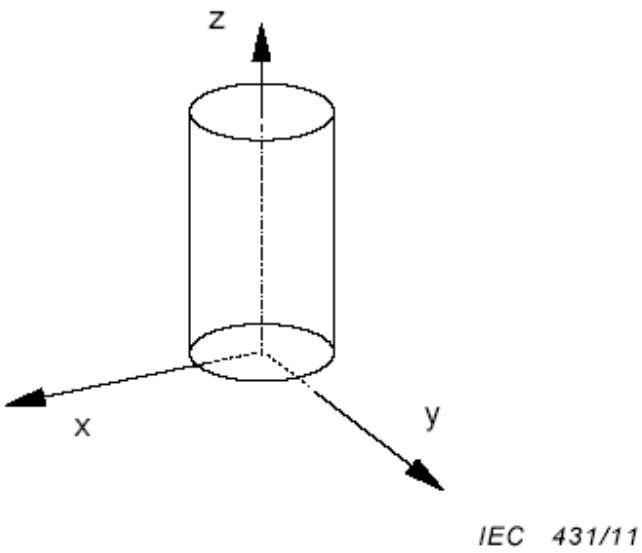

Figure 6 – XYZ axes for free fall

c) Requirements

There shall be no fire and no explosion during this test.

7 Information for safety

7.1 Safety precautions during handling of batteries

When used correctly, primary batteries with aqueous electrolyte provide a safe and dependable source of power. However, battery misuse or abuse may result in leakage, or in extreme cases, fire and/or explosion.

a) *Always insert batteries correctly with regard to the polarities (+ and –) marked on the battery and the equipment*

Batteries which are incorrectly placed into equipment may be short-circuited, or charged. This can result in a rapid temperature rise causing venting, leakage, explosion and personal injury.

b) *Do not short-circuit batteries*

When the positive (+) and negative (–) terminals of a battery are in electrical contact with each other, the battery becomes short-circuited. For example loose batteries in a pocket and/or handbag with keys or coins can be short-circuited. This may result in venting, leakage, explosion and personal injury.

c) *Do not charge batteries*
Attempting to charge a non-rechargeable (primary) battery may cause internal gas and/or heat generation resulting in venting, leakage, explosion and personal injury.

d) *Do not force discharge batteries*
When batteries are force discharged with an external power source, the voltage of the battery will be forced below its design capability and gases will be generated inside the battery. This may result in venting, leakage, explosion and personal injury.

e) *Do not mix old and new batteries or batteries of different types or brands*
When replacing batteries, replace all of them at the same time with new batteries of the same brand

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

and type.

When batteries of different brand or type are used together, or new and old batteries are used together, some batteries may be over-discharged due to a difference of voltage or capacity. This can result in venting, leakage and explosion and may cause personal injury.

f) *Exhausted batteries should be immediately removed from equipment and properly disposed of*
When discharged batteries are kept in the equipment for a long time, electrolyte leakage may occur causing damage to the appliance and/or personal injury.

g) *Do not heat batteries*
When a battery is exposed to heat, venting, leakage and explosion may occur and cause personal injury.

h) *Do not weld or solder directly to batteries*
The heat from welding or soldering directly to a battery may cause internal short-circuiting resulting in venting, leakage and explosion and may cause personal injury.

i) *Do not dismantle batteries*
When a battery is dismantled or taken apart, contact with the components can be harmful and may cause personal injury or possibly fire.

j) *Do not deform batteries*
Batteries should not be crushed, punctured, or otherwise mutilated. Such abuse may result in venting, leakage and explosion and cause personal injury.

k) *Do not dispose of batteries in fire*
When batteries are disposed of in fire, the heat build-up may cause explosion and personal injury. Do not incinerate batteries except for approved disposal in a controlled incinerator.

l) *Keep batteries out of the reach of children*
Especially keep batteries which are considered swallowable out of the reach of children, particularly those batteries fitting within the limits of the ingestion gauge as defined in Figure 7. In case of ingestion of a cell or a battery, the person involved should seek medical assistance promptly.

Dimensions in millimeters

PUBLIC REVIEW DRAFT

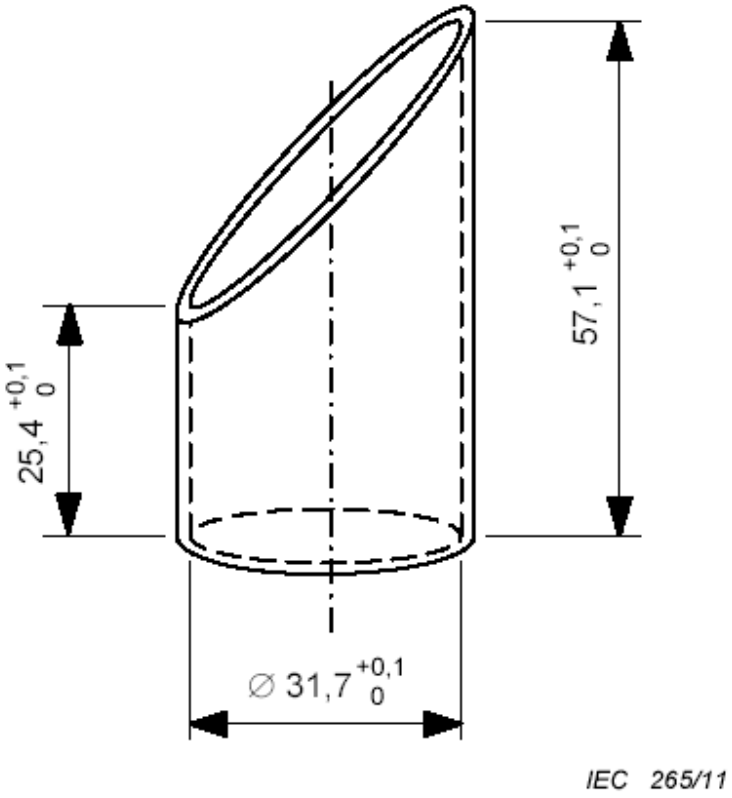

Figure 7 – Ingestion gauge (Inner dimensions)

m) *Do not allow children to replace batteries without adult supervision*

n) *Do not encapsulate and/or modify batteries*
Encapsulation, or any other modification to a battery, may result in blockage of the safety vent mechanism(s) and subsequent explosion and personal injury. Advice from the battery manufacturer should be sought if it is considered necessary to make any modification.

o) *Store unused batteries in their original packaging away from metal objects. If already unpacked, do not mix or jumble batteries.*
Unpacked batteries could get jumbled or get mixed with metal objects. This can cause battery short-circuiting which may result in venting, leakage and explosion and personal injury; one of the best ways to avoid this happening is to store unused batteries in their original packaging.

p) *Remove batteries from equipment if it is not to be used for an extended period of time unless it is for emergency purposes.*
It is advantageous to remove batteries immediately from equipment which has ceased tofunction satisfactorily, or when a long period of disuse is anticipated (e.g. still-cameras, photoflash, etc.). Although most batteries on the market today are provided with protective jackets or other means to contain leakage, a battery that has been partially or completely exhausted may be more prone to leak than one that is unused.

7.2 Packaging

The packaging shall be adequate to avoid mechanical damage during transport, handling and stacking. The materials and packaging design shall be chosen so as to prevent the development of unintentional electrical contact, corrosion of the terminals and some protection from the environment.

 © KEBS 2012 — All rights reserved

7.3 Handling of battery cartons

Rough handling of battery cartons may result in battery damage and impaired electrical performance and may result in leakage, explosion, or possibly fire.

7.4 Display and storage

a) *Batteries shall be stored in well-ventilated, dry and cool conditions*

High temperature or high humidity may cause deterioration of the battery performance or surface corrosion.

b) *Battery cartons should not be piled up in several layers (or should not exceed a specified height)*
If too many battery cartons are piled up, batteries in the lowest cartons may be deformed and electrolyte leakage may occur.

c) *When batteries are stored in warehouses or displayed in retail stores, they should not be exposed to direct sun rays for a long time or placed in areas where they get wet by rain*
When batteries get wet, their insulation resistance decreases, self-discharge may occur and rust may be generated.

d) *Do not mix unpacked batteries so as to avoid mechanical damage and/or short-circuit among each other*
When mixed together, batteries may be subjected to physical damage or overheating resulting from external short circuit. Leakage and/or explosion may then occur. To avoid these possible hazards, batteries should be kept in their packaging until required for use.

e) *See Annex A for additional details*

7.5 Transportation

When loaded for transportation, battery packages should be so arranged to minimise the risk of falling e.g. one from the top of another. They should not be stacked so high that damage to the lower packages occurs. Protection from inclement weather should be provided.

7.6 Disposal

a) *Do not dismantle batteries.*
b) *Do not dispose of batteries in fire except under conditions of controlled incineration.*
c) *Primary batteries may be disposed of via the communal refuse arrangements, provided that no local rules to the contrary exist.*
d) *Where there is provision for the collection of used batteries, the following should be considered:*
   - *Store collected batteries in a non-conductive container.*
   - *Store collected batteries in a well-ventilated area. Since some used batteries may still contain a residual charge, they could be short circuited, charged or force discharged and thereby evolve hydrogen gas. If collection containers and storage areas are not properly ventilated, hydrogen gas can build up and explode in the presence of an ignition source.*
   - *Do not mix collected batteries with other materials. Since some used batteries may still contain a residual charge, they could be short circuited, charged or force discharged. The subsequent possible heat generation can ignite flammable wastes such as oily rags, paper or wood and can cause a fire.*
   - *Consider protecting used battery terminals, particularly those batteries with high voltage, to preclude short circuits, charging and force discharging, for instance, by means of covering battery terminals with insulating tape.*
   - *Failure to observe these recommendations may result in leakage, fire, and/or explosion.*

8 Instructions for use

a) *Always select the correct size and grade of battery most suitable for the intended use. Information provided with the equipment to assist correct battery selection should be retained for reference.*
b) *Replace all batteries of a set at the same time.*

PUBLIC REVIEW DRAFT

c) *Clean the battery contacts and also those of the equipment prior to battery installation.*
d) *Ensure that the batteries are installed correctly with regard to polarity (+ and –).*
e) *Remove batteries from equipment which is not to be used for an extended period of time.*
f) *Remove exhausted batteries promptly.*

9 Marking

9.1 General (see Table 7)

With the exception of small batteries (see 9.2), each battery shall be marked with the following information:

a) designation, IEC or common;

b) year and month or week of manufacture, which may be in code, and the expiration of a guarantee period, which shall be in clear. The year and month or week of manufacture may be in code;

NOTE If the date of manufacture is in code, initial discharge tests shall be applied.

c) polarity of terminals (when applicable);

d) nominal voltage;

e) name or trade mark of the manufacturer or supplier;

f) cautionary advice.

9.2 Marking of small batteries (see Table 7)

a) Batteries designated in IEC as small, mainly category 3 and category 4 batteries have a surface too small to accommodate all markings shown in 9.1. For these batteries the designation 9.1a) and the polarity 9.1c) shall be marked on the battery. All other markings shown in 9.1 may be given on the immediate packing instead of on the battery.

b) For P-system batteries, 9.1a) may be on the battery, the sealing tab or the immediate packing. 9.1c) may be marked on the sealing tab and/or on the battery. 9.1b), 9.1d) and 9.1e) may be given on the immediate packing instead of on the battery.

c) Caution for ingestion of swallowable batteries shall be given. Refer to 7.1l) for details.

Table 7 – Marking requirements

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

Marking	Batteries with the exception of small batteries	Small batteries	
			P-system batteries
a) Designation, IEC or common	A	A	C
b) Expiration of a recommended usage period or year and month or week of manufacture. The year and month or week of manufacture may be in code	A	B	B
c) Polarity of the positive (+) terminal	A	A	D
d) Nominal voltage	A	B	B
e) Name or trade mark of the manufacturer or supplier	A	B	B
f) Cautionary advice	A	B[a]	B[a]
A: shall be marked on the battery. B: may be marked on the immediate packing instead on the battery. C: may be marked on the battery, the sealing tab or the immediate packing. D: may be marked on the sealing tab and/or on the battery.			
[a] Caution for ingestion of swallowable batteries shall be given. Refer to 7.1 l).			

PUBLIC REVIEW

© KEBS 2012 — All rights reserved

Annex A
(informative)
Additional information to 7.4

The purpose of this annex is to describe these good practices in general terms and, more specifically, to warn against procedures known from experience to be harmful. It takes the form of advice to battery manufacturers, distributors, users, and equipment designers.

Storage and stock rotation

a) For normal storage, the temperature should be between +10 ℃ and +25 ℃ and should never exceed +30 ℃. Extremes of humidity (over 95 % RH and below 40 % RH) for sustained periods should be avoided since they are detrimental to both batteries and packing. Batteries should therefore not be stored next to radiators or boilers nor in direct sunlight.

b) Although the storage life of batteries at room temperature is good, storage is improved at lower temperatures provided special precautions are taken. The batteries should be enclosed in special protective packing (such as sealed plastic bags or variants) which should be retained to protect them from condensation during the time they are warming to ambient temperature. Accelerated warming is harmful.

c) Batteries which have been cold-stored should be put into use as soon as possible after return to ambient temperature.

d) Batteries may be stored fitted in equipment or packages if determined suitable by the battery manufacturer.

e) The height to which batteries may be stacked is clearly dependent on the strength of the pack. As a general guide, this height should not exceed 1,5 m for cardboard packs or 3 m for wooden cases.

f) The above recommendations are equally valid for storage conditions during prolonged transit. Thus, batteries should be stored away from ship engines and not left for long periods in unventilated metal box cars (containers) during summer.

g) Batteries should be dispatched promptly after manufacture and in rotation to distribution centres and on to the users. In order that stock rotation (first-in, first-out) can be practised, storage areas and displays should be properly designed and packs should be adequately marked.

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

Annex B
(informative)
Battery compartment design guidelines

B.1 Background

B.1.1 General

In order to meet the ever-growing advances in battery-powered equipment technology, primary batteries have become more sophisticated in both chemistry and construction with resultant improvements to both capacity and rate capability. Resulting from these continuing developments and recognising the need for both safety and optimum battery performance it was established that the majority of reported battery failures resulted from electrical abuse generally arising from consumer accidental misuse.

The following text and figures are intended to aid the battery-powered equipment designer to significantly reduce or eliminate such battery failures.

B.1.2 Battery failures resulting from poor battery compartment design

Poor battery compartment design may lead to reversed battery installation or to short-circuiting of the batteries.

B.1.3 Potential hazards resulting from battery reversal

If a battery is reversed in a circuit with three or more batteries in series as shown in Figure B.1, the following potential hazards exist:

a) charging of the reversed battery;

NOTE The charging current limited by the external circuit/load.

b) gas generation within the reversed battery;

c) vent activation of the reversed battery;

d) leakage of electrolyte from the reversed battery.

NOTE Battery electrolytes are harmful to body tissues.

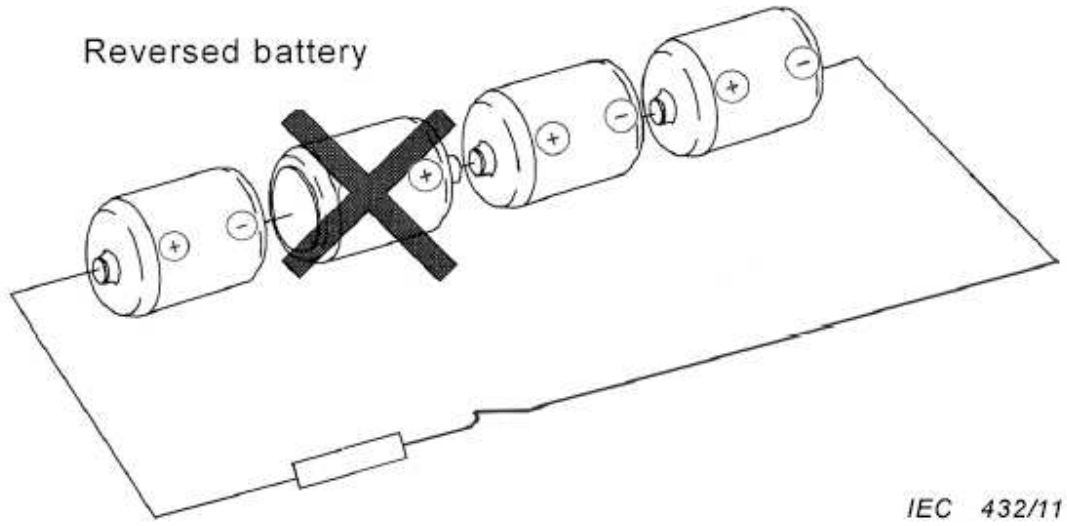

Figure B.1 – Example of series connection with one battery reversed

REVIEW DRAFT

B.1.4 Potential hazards resulting from a short circuit

a) Heat generation resulting from high current flow.
b) Gas generation.
c) Vent activation.
d) Electrolyte leakage.
e) Heat damage to insulating jackets (e.g. shrinkage).

NOTE Battery electrolytes are harmful to body tissues and generated heat can cause burns.

B.2 General guidance for appliance design

B.2.1 Key battery factors to be first considered

These guidelines are essentially directed toward cylindrical batteries with sizes ranging from R1 to R20. The battery systems involved are commonly referred to as alkaline manganese and zinc carbon. Whilst the two systems are interchangeable they should never be used in combination.

The following physical differences between the two systems and permitted design features should be noted during the early phases of battery compartment design.

a) The positive terminal of the alkaline manganese battery is connected to the battery case.
b) The positive terminal of the zinc carbon battery is insulated from the battery case.
c) Both battery types have an outer insulated jacket. This may be of paper, plastic or other non-conductive material. On occasion, the outer jacket may be metallic (conductive); in such instances this is insulated from the basic unit.
d) When forming the negative contact it should be noted that the corresponding battery terminal may be recessed. (For clarification refer to IEC 60086-1, 4.1.3). To ensure good electrical contact, completely flat negative equipment contacts should be avoided.
e) Under no circumstances should battery connectors or any part of the equipment circuitry come into contact with the battery jacket. Any design of battery compartment permitting this, risks the possibility of a short circuit.

NOTE For example, helical (not parallel) springs used for negative connection should compress uniformly when the battery is inserted and not bridge across to the battery jacket. (Spring connection to the positive terminal of a battery is not recommended.)

B.2.2 Other important factors to consider

a) It is recommended that companies producing battery-powered equipment should maintain close liaison with the battery industry. The capabilities of existing batteries should be taken into account at design inception. Whenever possible, the battery type selected should be one included in IEC 60086-2.
b) Design compartments so that batteries are easily inserted and do not fall out.
c) Design compartments to prevent easy access to the batteries by young children.
d) Dimensions should not be tied to a particular battery manufacturer as this can create problems when replacements of different origin are installed. Only consider the battery dimensions and tolerances defined within IEC 60086-2 when designing the battery compartment.
e) Clearly indicate the type of battery to use, the correct polarity alignment (+ and –) and directions for insertion.
f) Although batteries are very much improved regarding their resistance to leakage, it can still occasionally occur. When the battery compartment cannot be completely isolated from the equipment, it should be positioned so as to minimise possible equipment damage from battery leakage.
g) Design equipment circuitry such that equipment will not operate below 0,7 V per battery (0,7 V x n_S where n_S is the number of batteries connected in series). To continue discharging below this level may result in unfavourable chemical reactions within the battery/batteries resulting in leakage.

B.3 Specific measures against reversed installation

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

B.3.1 General

To overcome the problems associated with the reversed placement of a battery, consideration should be given at the design stage to ensure that batteries cannot be installed incorrectly or, if so installed, will not make electrical contact.

B.3.2 Design of the positive contact

Some suggestions for the R03, R1, R6, R14 and R20 size battery compartments are illustrated in Figures B.2 and B.3 below. Provision should also be made to prevent unnecessary movement of batteries within the battery compartment.

NOTE Battery contacts should be shielded to prevent contact during reverse installation.

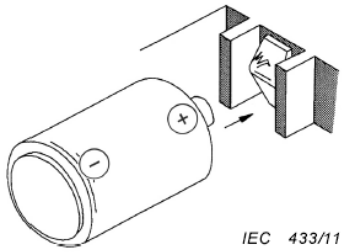

Figure B.2a – Correct insertion of the battery

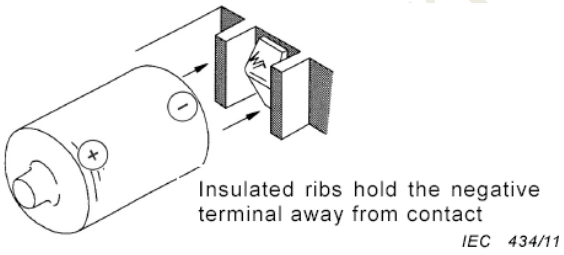

Figure B.2b – Incorrect insertion of the battery

Figure B.2 – Positive contact recessed between ribs

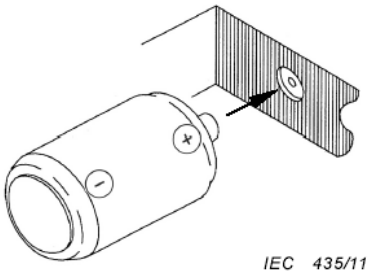

Figure B.3a – Correct insertion of the battery

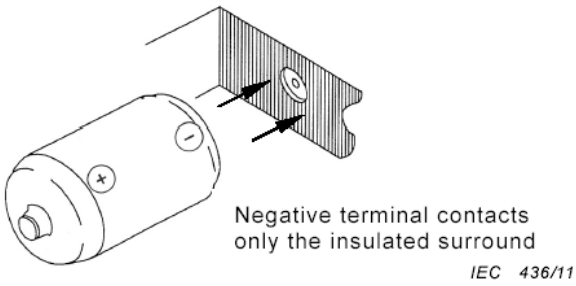

Figure B.3b – Incorrect insertion of the battery

Figure B.3 – Positive contact recessed within surrounding insulation

B.3.3 Design of the negative contact

The following suggestion is given for R03, R1, R6, R14 and R20 size battery compartments (see Figure B.4).

PUBLIC REVIEW DRAFT

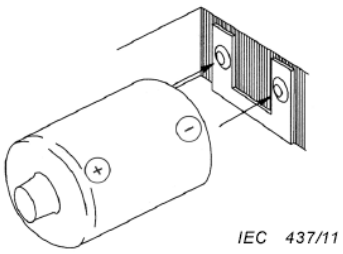

Figure B.4a – Correct insertion of the battery

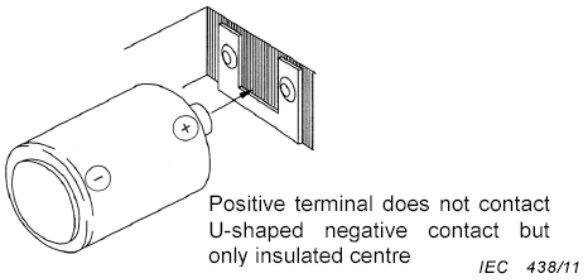

Figure B.4b – Incorrect insertion of the battery

Figure B.4 – Negative contact U-shaped to ensure no positive (+) battery contact

B.3.4 Design with respect to battery orientation

In order to avoid reverse insertion of batteries, it is recommended that all batteries have the same orientation. Examples are shown in Figures B.5a and B.5b.

Figure B.5a shows the preferred battery arrangement inside a device while Figure B.5b shows an alternative recommendation.

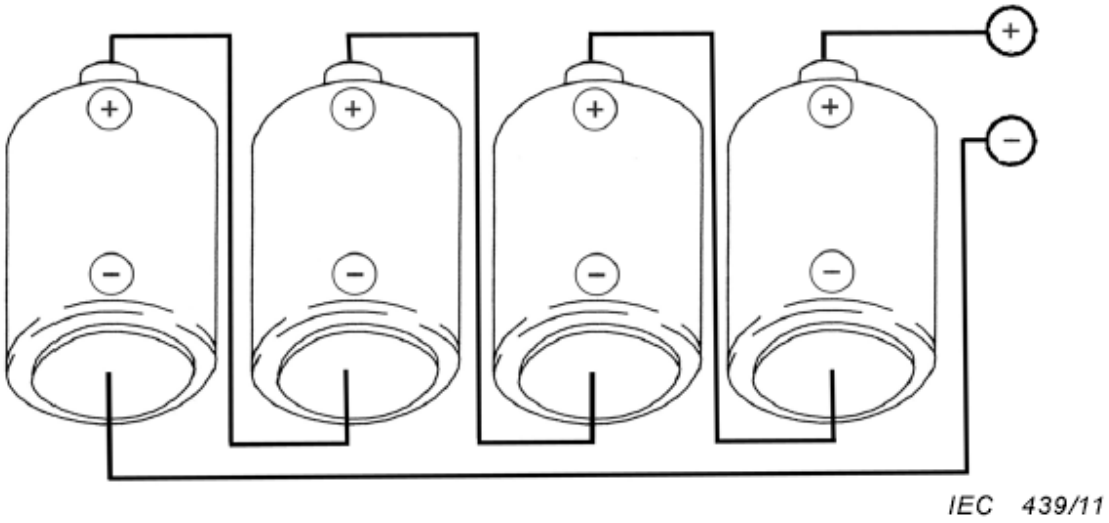

NOTE Protection of the positive contact should be as shown in Figures B.2 and B.3.

Figure B.5a – Preferred battery orientation

 © KEBS 2012 — All rights reserved

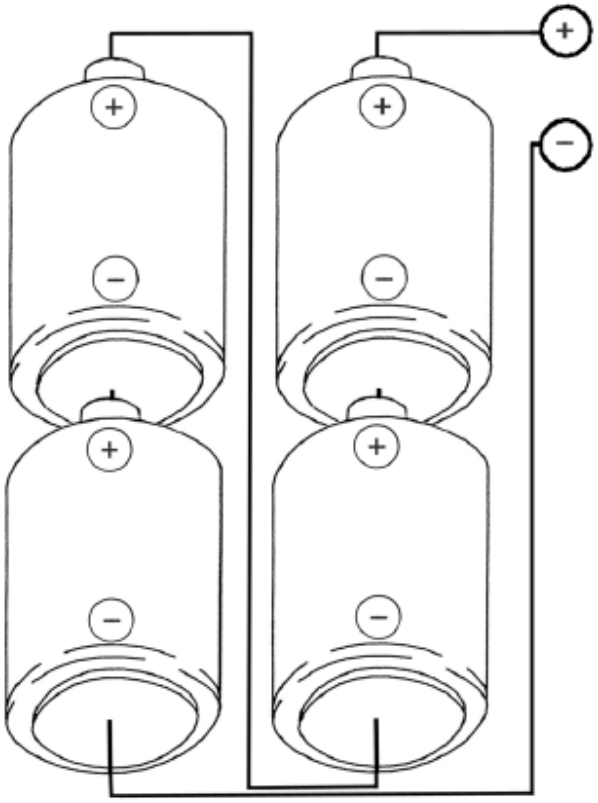

NOTE 1 Protection of the contacts should be as shown in Figures B.2 or B.3 for the positive and Figure B.4 for the negative contact.
NOTE 2 This arrangement (Figure B.5b) is only considered practical for R14 and R20 size batteries due to the small negative terminal area (dimension C of the relevant specification) of the other sizes.

Figure B.5b – Alternative recommendation for battery orientation

Figure B.5 – Design with respect to battery orientation

B.3.5 Dimensional considerations

Table B.1 provides critical dimensional details relating to the battery terminals and the recommended dimensions for the devices positive contact. By making reference to Figure B.6, and designing in accordance with the dimensions shown in Table B.1, subsequent reversal of a battery, such that its negative terminal is presented to the devices positive contact, will result in a 'fail safe' situation, i.e. there will be no electrical contact.

Table B.1 – Dimensions of battery terminals and recommended dimensions of the positive contact of an appliance in Figure B.6

Dimensions in millimetres

PUBLIC REVIEW DRAFT

Relevant dry batteries	Dimension of the negative battery terminal	Dimension of the positive battery terminal		Recommended dimensions of the positive contact of an appliance in Figure B.6	
	d_6[a] (minimum)	d_3[a] (maximum)	h_3[a] (minimum)	X	Y
R20, LR20	18,0	9,5	1,5	9,6 – 11,0	0,5 – 1,4
R14, LR14	13,0	7,5	1,5	7,6 – 9,0	0,5 – 1,4
R6, LR6	7,0	5,5	1,0	5,6 – 6,8	0,4 – 0,9
R03, LR03	4,3	3,8	0,8	3,9 – 4,2	0,4 – 0,7
R1, LR1	5,0	4,0	0,5	4,1 – 4,9	0,1 – 0,4
[a] Refer to IEC 60086-2.					

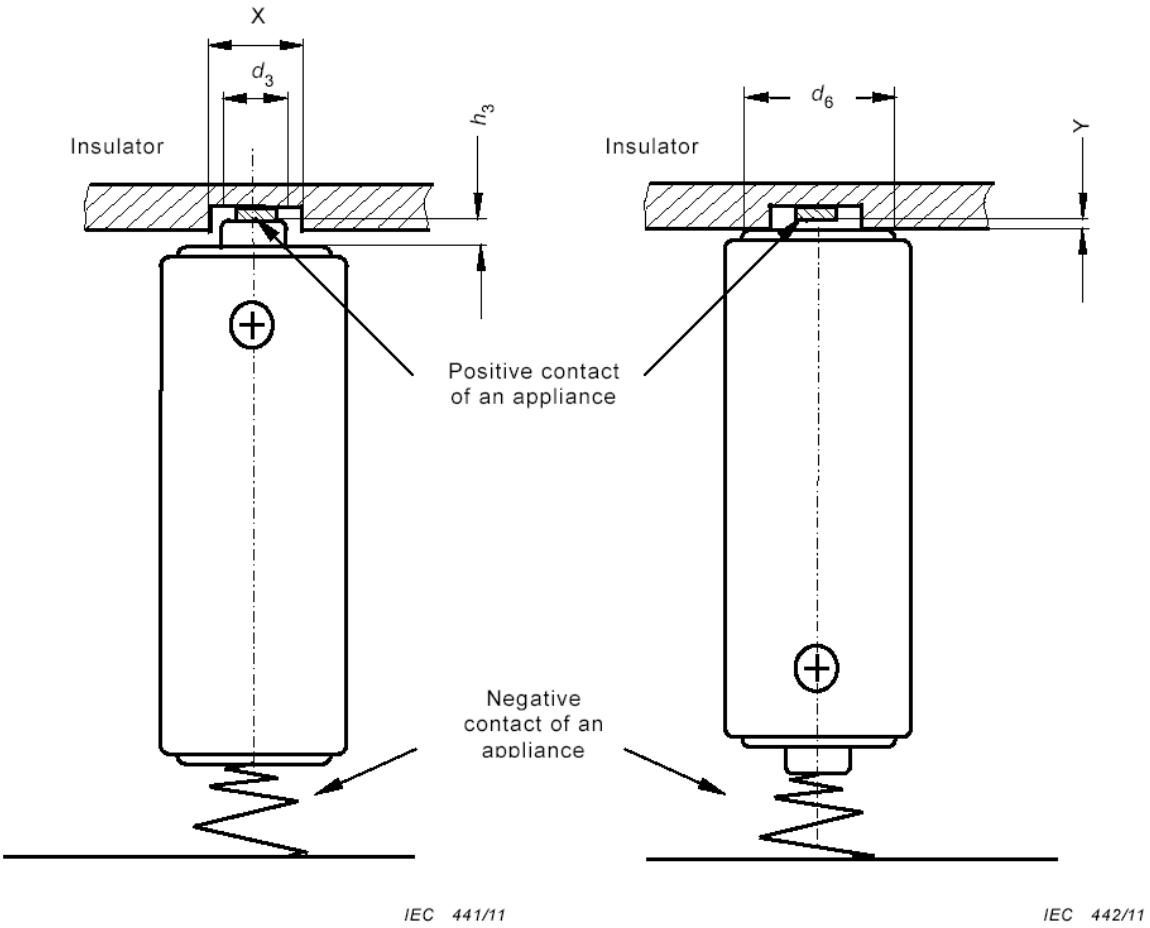

Figure B.6a – Correct insertion **Figure B.6b – Incorrect insertion**

NOTE Positive contact of an appliance is recessed within surrounding insulation.

Figure B.6 – Example of the design of a positive contact of an appliance

The diameter of the recessed hole is larger than the diameter (d_3) of the positive battery terminal but is smaller than the diameter (d_6) of the negative battery terminal. The insertion of the battery in Figure B.6a is correct. In Figure B.6b the reverse insertion of the battery is shown; in this instance the negative

 © KEBS 2012 — All rights reserved

terminal of the battery only contacts the surrounding insulation thereby preventing electrical contact.

The letter codes in Figure B.6 are as follows:

d_6 minimum outer diameter of the negative flat contact surface;

d_3 maximum diameter of the positive contact within the specified projection height;

h_3 minimum projection of the flat positive contact;

X Diameter of the recessed hole as a positive contact with the positive battery terminal. X should be bigger than d_3 but smaller than d_6;

Y Depth of the recessed hole as a positive contact with the positive battery terminal. Y should be smaller than h_3.

B.4 Specific measures to prevent short-circuiting of batteries

B.4.1 Measures to prevent short-circuiting due to battery jacket damage

In alkaline manganese batteries, the steel case, which is covered by an insulating jacket (see B.2.1 c), has the same voltage as the positive terminal. Should the insulating jacket be cut or pierced by any conductive circuitry within an appliance, a short circuit may occur as shown in Figure B.7. (It should be noted that the damage described above can be aggravated if the appliance is subjected to physical abuse, e.g. abnormal vibration, dropping, etc.).

NOTE 1 The potential hazards resulting from a short circuit are defined in B.1.3.

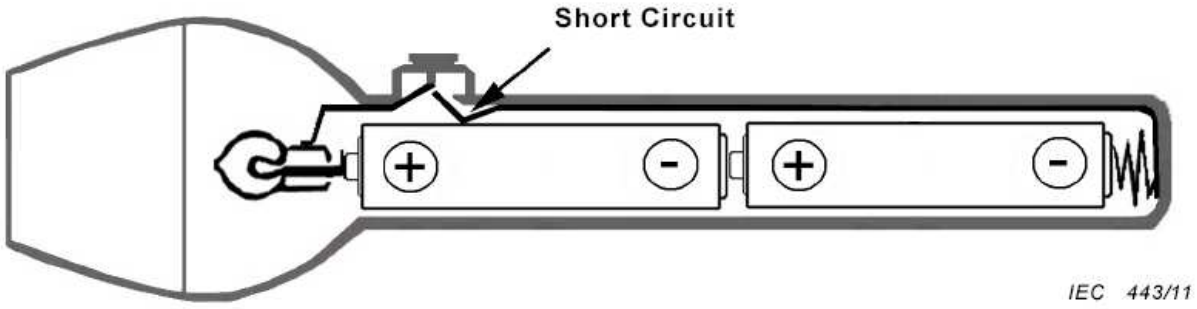

Figure B.7 – Example of a short circuit, a switch is piercing the battery insulating jacket

NOTE 2 Whilst the example shown in Figure B.7 commonly relates to alkaline manganese battery systems, the batteries addressed in this annex are interchangeable (see B.2.1).

Prevention: insulating material positioned as shown in Figure B.8 prevents the switch from damaging the battery jacket.

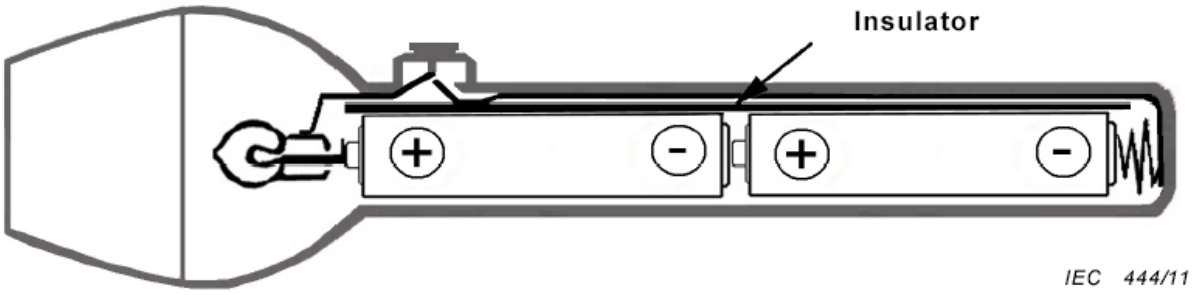

Figure B.8 – Typical example of insulation to prevent short circuit

It is also essential that no part of the equipment or equipment circuitry, including rivets or screws, used to secure the battery contacts etc. is allowed to contact the battery case/jacket.

B.4.2 Measures to prevent external short-circuit of a battery caused when coiled spring contacts are employed for battery connection

Placement of a battery (positive (+) end foremost) as shown in Figure B.9 may result in distortion of the negative (–) spring contact and subsequent cutting and piercing of the battery insulating jacket when a battery is inserted against the spring as shown in Figure B.10.

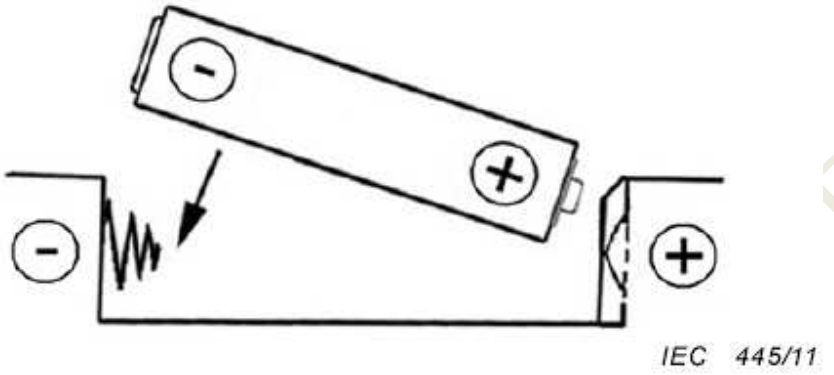

Figure B.9 – Insertion against spring (to be avoided)

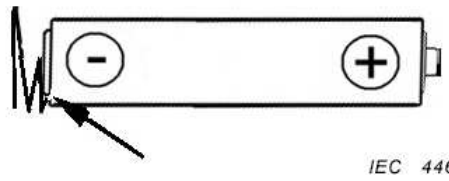

Figure B.10a – Spring slides underneath the jacket and contacts the metal can

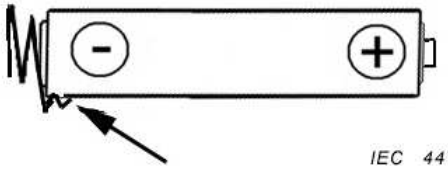

Figure B.10b – Jacket is punctured

Figure B.10 – Examples showing distorted springs

Prevention: in order to eliminate the possible incidents shown in Figure B.10, it is recommended that the design of the battery compartment allows the battery, when correctly inserted (negative terminal first), to evenly compress the coil spring as shown in Figure B.11. The insulated guide above the negative (–) connections in Figure B.11 ensures this.

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

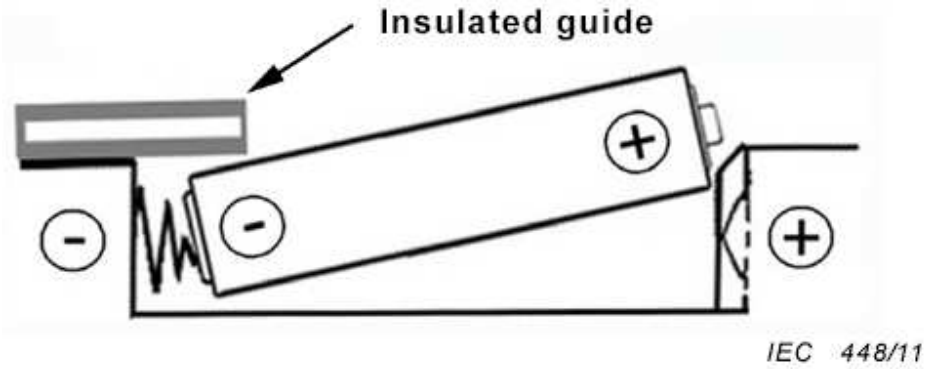

Figure B.11 – One example of protected insertion

The end of the spring coil i.e. that part in final contact with the battery should be bent toward the centre of the coil so that no sharp edges are presented to the battery jacket.

The spring wire should be of sufficient diameter as specified in Table B.2. The spring contact pressure should be sufficient to ensure that the batteries make and maintain good electrical contact at all times. However, the spring contact pressure should not be so great as to preclude easy battery insertion and removal. Excessive spring contact pressure can cause cutting or piercing of the insulating jacket or contact deformation.

This can lead to a short circuit and/or leakage.

Table B.2 contains details on the recommended diameters of the spring wire.

Spring coil contacts should only contact the negative terminals of cylindrical batteries.

Table B.2 – Minimum wire diameters

Battery type		Minimum wire diameter mm
R20	LR20	0,8
R14	LR14	0,8
R6	LR6	0,4
R03	LR03	0,4
R1	LR1	0,4

B.5 Special considerations regarding recessed negative contacts

IEC 60086-2 specifies the maximum recess of the negative battery terminal from the external jacket. Many R20, LR20, R14 and LR14 batteries have a recessed negative terminal. Some batteries are provided with projections of insulating resin on the negative terminal in order to prevent electrical contact if the battery is reversed.

© KEBS 2012 — All rights reserved

NOTE It is imperative that the above shapes and dimensions of negative battery terminals are taken into account during the early stage of the design of the negative contact of an appliance. Specific precautions of three (3) kinds of contacts which are generally used are described in the following.

a) When a spring coil is used as the negative contact of an appliance: the diameter of the coil which interfaces with the battery should be smaller than d_6, where d_6 is the external diameter of the contact surface of the negative battery terminal.
b) Where sheet metal is cut and formed to make a negative contact (see Figure B.12), it is essential that the dimensions h_4 and d_6, as defined in Table B.3, are noted and acted upon. As shown in Figure B.12 a projection/pip should be provided. This projection/pip should be of sufficient depth to overcome any recess in the battery terminal (dimension h_4). Failure to follow this advice may result in loss of battery contact.
c) Where it is proposed to employ a flat metal plate as the negative contact of an appliance, it is essential that one or more 'pips'/projection(s) are provided to ensure battery contact. The projection(s) should be of sufficient depth to overcome any recess in the negative terminal of the battery (dimension h_4) and be placed within the confines of the battery terminal contact area (dimension d_6).

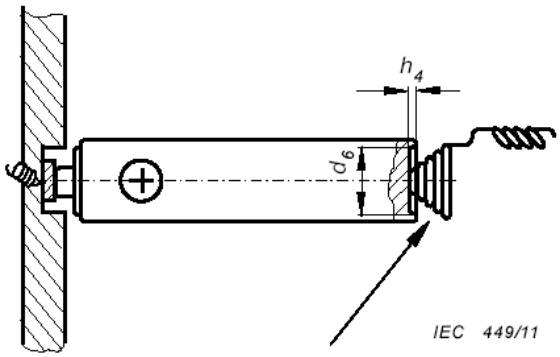

Figure B.12a – Spring coil

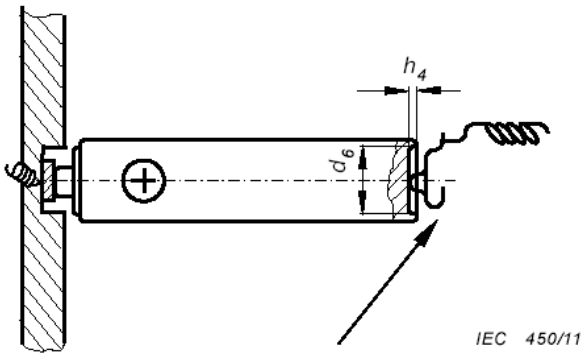

Figure B.12b – Plate spring contact

Battery type

Figure B.12 – Example of negative contacts

Table B.3 – Dimensions of the negative battery terminal

Dimensions in millimetres

Battery type	Maximum recessed dimension of negative battery terminal h_4[a]	External diameter of the contact surface of negative battery terminal d_6[a]
R20, LR20	1,0	18,0
R14, LR14	0,9	13,0
R6, LR6	0,5	7,0
R03, LR03	0,5	4,3
R1, LR1	0,2	5,0
[a] Reference IEC 60086-2.		

It should be stressed that battery compartment dimensions should not be tied to dimensions and tolerances of a particular manufacturer as this can create problems if replacements of different origin are installed.

For dimensional details, particularly those related to the positive and negative terminals, reference

 © KEBS 2012 — All rights reserved

should be made to Figure 1a and Figure 1b of KS 184-2 and the relevant battery specifications contained in KS 184-2.

B.6 Waterproof and non-vented devices

It is important that hydrogen gas generated in the batteries is either removed by recombination reaction or allowed to escape; otherwise a spark could ignite the entrapped hydrogen/air mixture resulting in an explosion of the device. The advice of the battery manufacturer should be sought at the design stage of such applications.

B.7 Other design considerations

a) Only the battery terminals should physically contact the electric circuit. Battery compartments should be electrically insulated from the electric circuit and positioned so as to minimise possible damage and/or risk of injury resulting from battery leakage.

b) Much equipment is designed to operate with alternative power supplies (e.g. mains, additional batteries, etc.) and this is particularly relevant to primary battery memory back-up applications. In these situations, the circuitry of the equipment should be so designed to either
   1) prevent charging of the primary battery, or
   2) include primary battery protective devices, for example a diode, such that the reverse charging current from the protective device(s) to which the primary battery would be subjected does not exceed that recommended by the battery manufacturer.

   Any intended protective device circuit should be selected so as to be appropriate to the type and electrochemical system of the primary battery concerned and preferably not subject to single component failure. It is recommended that equipment designers obtain advice from the battery manufacturer concerning the primary battery memory back-up protection device circuit.

   Failure to observe these precautions may lead to short service life, leakage or explosion.

c) Positive (+) and negative (–) battery contacts should be visibly different in form to avoid confusion when inserting batteries.
d) Select terminal contact materials with the lowest electrical resistance and compatible with battery contacts.
e) Battery compartments should be non-conductive, heat resistant, non-flammable and have good heat radiation. They should not deform when a battery is inserted.
f) Equipment designed to be powered by air-depolarised batteries of either the A or P system should provide for adequate air access. For the A system, the battery should preferably be in an upright position during normal operation.
g) Parallel connections are not recommended since an incorrectly placed battery causes continuous discharge of the batteries even if the device is not switched on. To overcome the problem of reversed placement described above and with the end user in mind, consideration should be given to the arrangement in Figure B.5a and Figure B.5b.

WARNING In some parallel battery circuits the discharge current can be similar to that of a battery under short circuit conditions.

Potential hazards arising from the reversal of a battery in a parallel circuit are described in B.1.3.

NOTE In extreme cases, battery explosion may occur.

h) Series connection of batteries with multiple voltage outputs as shown in Figure B.13 is not recommended since a discharged section may be driven into reverse voltage.

EXAMPLE In Figure B.13, two batteries are discharging through resistor R1; if, following their discharge, the switch is positioned toward the R3 circuit, forced discharging of the former two batteries may occur.

PUBLIC REVIEW DRAFT

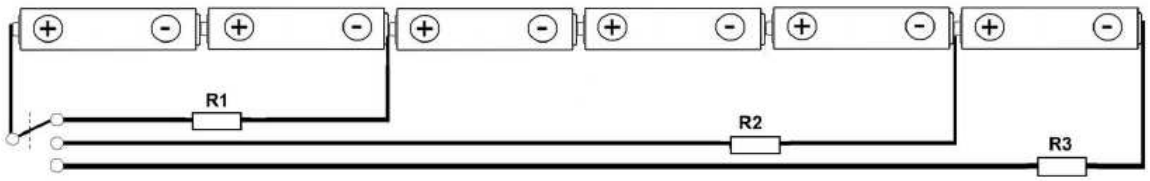

Figure B.13 – Example of series connection of batteries with voltage tapping

Potential hazards arising from forced discharging (driving into reverse voltage).

1) Gas generation within the forced discharged battery/batteries.
2) Vent activation
3) Electrolyte leakage

NOTE Battery electrolytes are harmful to body tissues

PUBLIC REVIEW DRAFT

 © KEBS 2012 — All rights reserved

Annex C
(informative)
Safety pictograms

C.1 Overview

Cautionary advice to fulfil the marking requirements in this standard has, on a historical basis, been in the form of written text. In recent years, there has been a growing trend toward the use of pictograms as a complementary or alternative means of product safety communication.

The objectives of this annex are: (1) to establish uniform pictogram recommendations that are tied to long-used and specific written text, (2) to minimize the proliferation of safety pictogram designs, and (3) to lay the foundation for the use of safety pictograms *instead* of written text to communicate product safety and cautionary statements.

C.2 Pictograms

The pictogram recommendations and cautionary advices are given in Table C.1.

Table C.1 – Safety pictograms

Reference	Pictogram	Cautionary advice
A		DO NOT CHARGE
B		DO NOT DEFORM / DAMAGE
C		DO NOT DISPOSE OF IN FIRE
D		DO NOT INSERT INCORRECTLY
NOTE The grey shading highlights a white margin appearing when the pictogram is printed on coloured or black background.		

© KEBS 2012 — All rights reserved

Table C.1 – Safety pictograms *(continued)*

Reference	Pictogram	Cautionary advice
E		KEEP OUT OF REACH OF CHILDREN
F		DO NOT MIX DIFFERENT TYPES OR BRANDS
G		DO NOT MIX NEW AND USED
H		DO NOT OPEN / DISMANTLE
I		DO NOT SHORT CIRCUIT
J		INSERT CORRECTLY

NOTE The grey shading highlights a white margin appearing when the pictogram is printed on coloured or black background.

C.3 Instructions for use

The following instructions are provided for use of the pictograms.

a) Pictograms shall be clearly legible.
b) Whilst colours are permitted, they shall not detract from the information displayed. If colours are used, the background of pictogram J should be blue and the circle and diagonal bar of the other pictograms should be red.
c) Not all of the pictograms need to be used together for a particular type or brand of battery. In particular, pictogram D and J are meant as alternatives for a similar purpose.

 © KEBS 2012 — All rights reserved

Bibliography

KS 184-3, *Primary batteries – Part 3: Watch batteries*

KS 184-4, *Primary batteries – Part 4: Safety of lithium batteries*

ISO/IEC Guide 51:1999, *Safety aspects – Guidelines for their inclusion in standards*

IEC 60050-482:2004, *International Electrotechnical Vocabulary – Part 482: Primary and secondary cells and batteries*

PUBLIC REVIEW DRAFT